

# Activated Carbon Monolith Derived from Coconut Husk Fiber as Electrode Material for Supercapacitor Energy Storage

*by* Rika Taslim

---

**Submission date:** 07-Dec-2020 10:50AM (UTC+0700)

**Submission ID:** 1466968525

**File name:** Taer\_2020\_J.\_Phys.\_\_Conf.\_Ser.\_1655\_012164.pdf (1.57M)

**Word count:** 3567

**Character count:** 18855

## Activated Carbon Monolith Derived from Coconut Husk Fiber as Electrode Material for Supercapacitor Energy Storage

Erman Taer<sup>1,\*</sup>, Verdy Manoto Naipospos<sup>1</sup>, Rika Taslim<sup>2</sup>, Agustino<sup>1</sup>, Apriwandi<sup>1</sup>

<sup>1</sup>Department of Physics, University of Riau, 28293 SimpangBaru, Riau, Indonesia

<sup>2</sup>Departement of Industrial Engineering, State Islamic University of Sultan Syarif Kasim, 28293 Simpang Baru, Riau, Indonesia

\*erman.taer@lecturer.unri.ac.id

**Abstract.** Biomass-derived porous activated carbon materials have been receiving considerable attention in energy-storage devices especially for supercapacitor due to abundant, renewable, sustainable, and cost-effective production. In this study, porous activated carbon material with monolithic form has been successfully prepared from coconut husk fiber through one-stage integrated pyrolysis and  $\text{ZnCl}_2$  impregnation. Different physical activation temperature is the main focus in this study including 750, 800, 850, and 900 °C. The reduction of monolith dimensions such as mass, diameter, thickness and density have been reviewed as physical properties. Furthermore, the supercapacitor cells were performed with cyclic voltammetry t 1 M  $\text{H}_2\text{SO}_4$  aqueous electrolyte at low scan rate of 1 mV s<sup>-1</sup>. The supercapacitor device based on the CFM-800 samples exhibited highest specific capacitance of 216 F g<sup>-1</sup>. This sample also performed a promising performance with an energy density of 30.00 Whkg<sup>-1</sup> and a high power density of 108.57 Wkg<sup>-1</sup>. These results demonstrate that the coconut husk fiber has been a high potential to as raw material for porous activated carbon monolith through low cost, vehicle and short-time processing with high-performance supercapacitors energy storage.

### 1. Introduction

Today, coconut is a valuable commodity due to its various uses including coconut oil, shredded coconut, coconut milk, butter, and super-hydrating coconut water. In 2016 and 2017, Indonesia was the largest coconut producer in the world with a total production of 18,983,378 tons in 2017[1]. However, coconut production produces a lot of waste, especially coconut husk which has about 85% from coconut plant. The fiber from coconut coir known as coconut coir is actually very versatile and can be used in a variety of different products such as growing media, materials for making mats and brushes, components for mattresses, and floor tiles [2]. As a waste management perspective, the coconut husk has high lignocellulose which considered as a key to valuable higher development.

Biomass waste containing lignocellulose could act as the main source of activated carbon material due to it is a low cost, easy to produce, renewable and sustainable, and has excellent physico-chemical properties[3,4]. Lignocellulosic waste could be converted into activated carbon through various processes such as pyrolysis, hydrothermal, chemical [27] activation, carbonization, and physical activation[5,6]. Currently, many researchers focus more on the use of biomass waste as activated carbon for electrode materials as an energy storage device, especially supercapacitors, such as bamboo [7,8], mangosteen [9,10], sakura flower[11], and tobacco wastes[12,13]. They reported that the resulting activated carbon electrode material with high capacitive in the range of 200-300 Fg<sup>-1</sup>. Furthermore, similar studies carried out to convert the from coconut husk fiber to activated carbon



Content from this work may be used under the terms of the [Creative Commons Attribution 3.0 licence](https://creativecommons.org/licenses/by/3.0/). Any further distribution of this work must maintain attribution to the author(s) and the title of the work, journal citation and DOI.

Published under licence by IOP Publishing Ltd

which has the potential as a absorber that could solve the many wastewater problem[14,15]. Recently, our research group has successfully prepared the porous carbon monolith based on coconut husk as raw material through KOH impregnation in high-temperature physical activation [16]. This is performed that coconut husk can be converted into activated carbon for the supercapacitor electrode material. Moreover, the specific capacitance generated is still low at around of  $184 \text{ Fg}^{-1}$ . This may be due to the waste from coconut husk fiber that has not been separated from the coir.

In this study, we focused to investigate the electrochemical behavior of activated carbon derived from coconut husk fiber as an electrode material for supercapacitors. Coconut husk was pre-treated to separate coir from their husk fiber. The  $\text{ZnCl}_2$  in 0.5 M concentration was selected as a chemical activating agent. The pyrolysis process is carried out in one-stage integrated pyrolysis both carbonization and physical activation. The temperature of physical activation was varied of 750, 800, 850, and 900 °C, respectively. Activated carbon is prepared in a monolith/pellet form without the addition of adhesives materials such as PVDF and PTFE. The cyclic voltammetry analysis was employed to evaluate the capacitive properties of the symmetric supercapacitor cell. Furthermore, reduction of mass, thickness, diameter, and density were also reviewed to evaluate the initial physical properties of activated carbon monolith derived from coconut husk fiber.

## 2. Methods

The activated carbon monolith derived from coconut husk fiber through  $\text{ZnCl}_2$  activation and one-stage-integrated pyrolysis. Coconut husk waste collected from traditional market in Pekanbaru, Riau province were sundried for two days and continued in vacuum oven at a temperature of 110 °C. Furthermore, the coconut husk waste is pre-treated to separate the fibers from the coir with boiled in electrical stove for 20 minutes. Subsequently, coconut husk fibers were pre-carbonized in a vacuum oven at a temperature of 250 °C. Furthermore, pre-carbonized samples converted into powder by using mortar and milling tools and it followed by  $\text{ZnCl}_2$  impregnation in a hot plate at a temperature of 80 °C. Next, the carbon powders converted into monolith/pellet by using hydraulic press. The samples were prepared in 20 monoliths and subsequently pyrolyzed in one-stage integrated pyrolysis which begins with carbonized in an  $\text{N}_2$  gas environment from a temperature of 30 °C to 600 °C and followed by physical activation at a high temperature[17]. The temperatures of physical activation were varied of 750, 800, 850, and 900 °C, respectively. Based on the differences in chemical activation treatments, the samples were labelled CFM-750, CFM-800, CFM-850 and CFM-900, respectively. For more details of bamboo activated carbon preparation are shown in Figure 1. Finally, the activated carbon monoliths were neutralized with distilled water and polished in 0.2 mm thickness for electrode tested.


The initial physical properties of carbon monolith were evaluated in reduction of mass, diameter, thickness and density of the sample. The density was calculated with standard equation. Moreover, the electrochemical behavior were performed by using the cyclic voltammetry method (CV, CV UR Rad-Er 5841 instrument, calibrated with VersaStat II Princeton Applied Research, an error of  $\pm 6.05\%$ ) at Materials Laboratory, Department of Physics, University of Riau, Indonesia. The symmetric supercapacitor cells were assembled in the coins-type including activated carbon monolith as material electrodes, 1 M  $\text{H}_2\text{SO}_4$  aqueous electrolyte, and egg duck shell membrane as separator. The electrochemical behaviors were calculated by using the standard equations based on CV curve data's [18,19].

$$C_{sp} = \frac{2.I}{s.m} \quad (1)$$

$$E = \frac{1}{2} \cdot C_{sp} \cdot V^2 \cdot \frac{1000}{3600} \quad (2)$$

$$P = \frac{E}{\Delta t} \cdot 3600 \quad (3)$$

Were,  $I$  is the average current (A),  $s$  is the scan rate ( $\text{mV s}^{-1}$ ),  $m$  is the average mass of the electrodes (g),  $V$  is voltage window (V), and  $\Delta t$  is time for discharge process (s).

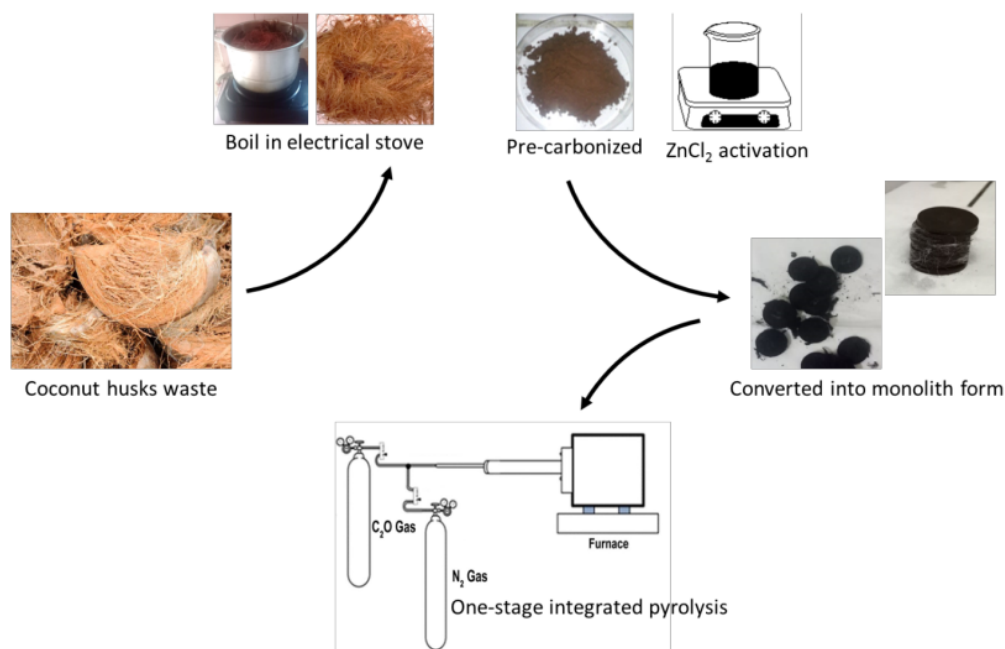


**Figure 1.** Schematic of production of activated carbon monolith derived from coconut husk fiber.

### 3. Results and Discussion

Reduction of mass, diameter, thickness, and density were a frequent initial review to evaluate the physical properties of activated carbon monoliths, as have been reported in previous studies. One-stage integrated pyrolysis both carbonization and physical activation and  $\text{ZnCl}_2$  activation contributed to converting the raw material to porous activated carbon and it caused a reduction in the dimensions of the monolithic samples. In the one-stage integrated pyrolysis process, the carbon precursors are first carbonized in an inert atmosphere from  $21^\circ\text{C}$  to  $600^\circ\text{C}$  to remove most of the volatile matter and followed by partial gasification using  $\text{CO}_2$  gas at a different level temperature of  $750\text{--}900^\circ\text{C}$ [6]. Initially, the active oxygen in the activating agent burns out the impurity byproducts of the pyrolysis products trapped in the pores, leading to the opening of some of the closed pores[20]. Then the micropores structure was developed in a larger direction such as mesopores and macropores depending upon the level of physical activation temperature[21].

As shown in Figure 2a, mass, diameter, and thickness exhibit a greater reduction as well as an increase in physical activation temperature from  $750\text{--}900^\circ\text{C}$ . This is caused by increasing the physical activation temperature erodes the wall of micropores and developed larger pores and it causes a reduction in mass. Monolith average mass were showed the greatest reduction of 73% and followed by diameter and thickness of 23% and 14%, respectively. The mass reduction for the CFM-750, CFM-800, CFM-850, and CFM-900 samples were 61.25%, 64.96%, 74.54%, and 75.31%, respectively. An increasing activation temperature could increase the reduction in mass. Based on the mass, diameter, and thickness data, the density could be calculated using a standard formula. The increase in physical activation temperature also affects the density of the monolith sample, as shown in Figure 2b. After the pyrolysis process, the reduced monolith density is  $0.7499\text{ g cm}^{-3}$ ,  $0.8488\text{ g cm}^{-3}$ ,  $0.5710\text{ g cm}^{-3}$ , and  $0.7158\text{ g cm}^{-3}$  for CFM-750, CFM-800, CFM-850, and CFM-900, respectively with a mean standard deviation of 0.081. This result was similar with other study in different biomass such as activated


carbon monolith derived from durian shell [22], pineapple crown [23], and pandanus tectorius leaves [24].

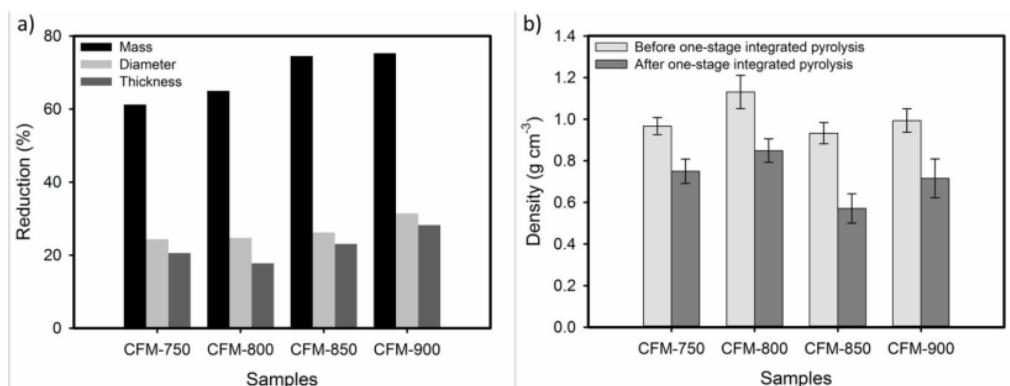

**Figure 2.** (a) Reduction of mass, thickness, and mass, and (b) Density of carbon monolith before and after physical activation.


The cyclic voltammetry (CV) method was evaluated in a potential window to evaluate the capacitive behaviours of the porous carbon monoliths as an electrode material. The samples of CFM-750, CFM-800, CFM-850, and CFM-900 carbon monoliths were performed as the electrode monolith to evaluate the coconut husk fiber as raw material of porous carbon electrodes in supercapacitor application. The symmetric supercapacitor cells were tested in coin layers at a potential window of 0-1.0 V in 1 M  $\text{H}_2\text{SO}_4$  aqueous electrolyte. In Figure 3a, all samples performed the CV curves of the different samples at a low scan rate of  $1 \text{ mV s}^{-1}$ . All the curves exhibited quasi-rectangular CV shapes, which correlated with a large part of electrical double-layer capacitor based on ideal ionic adsorption and desorption behaviours [22,25]. Moreover, the CV integral area indicates the specific capacitance of the carbon monolith electrode. Clearly, the CFM-800 sample possesses the largest CV integral area than other which illustrated that CFM-800 showed the highest specific capacitance of  $216 \text{ F g}^{-1}$ , followed by CFM-750, CFM-850, and CFM-900 of  $202 \text{ F g}^{-1}$ ,  $192 \text{ F g}^{-1}$ , and  $147 \text{ F g}^{-1}$ , respectively. However, the current density of CFM-750, CFM-800, and CFM-850 were significant increase in low potential window of  $<0.1 \text{ V}$  than CFM-900. This is confirmed that CFM-750, CFM-800, and CFM-850 have a good combination pores between micropores and mesopores that is suitable for ion diffusion on morphology surface which contribute to more electric double-layer [10,26]. In contrast with CFM-750, CFM-800, CFM-850, and CFM-900 showed a significant increase of specific capacitance in higher potential window of 0.4-1.0 V which due to the fact that the initial micropores developed tend to be larger and lead to the formation of combination mesopores and macropores [27]. Based on this result, the physical activation temperatures are affected to electrochemical behaviour of supercapacitor cell. Increasing the temperature from  $750^\circ\text{C}$  to  $800^\circ\text{C}$  could enhance the specific capacitance from  $202 \text{ F g}^{-1}$  to  $216 \text{ F g}^{-1}$ . Furthermore, in higher temperature, the specific capacitance is reduced from  $216 \text{ F g}^{-1}$  to  $147 \text{ F g}^{-1}$  for  $800^\circ\text{C}$  to  $900^\circ\text{C}$ . This is caused by higher temperature could develop the initial pores tend to be larger and lead to the new large formation of pores.



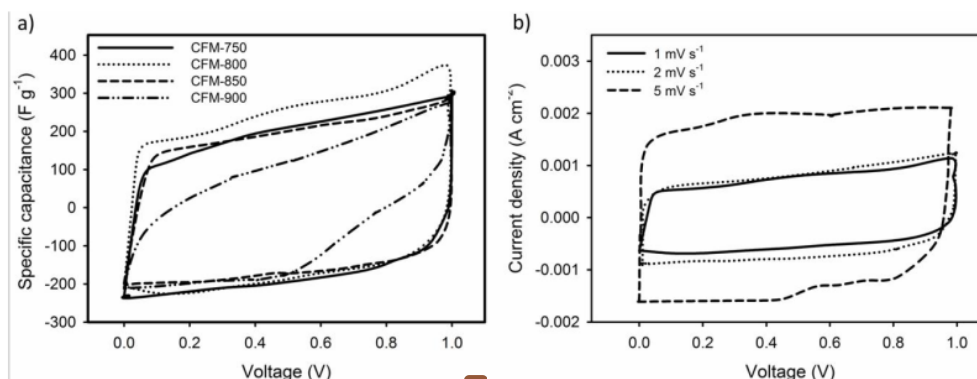

**Figure 3.** (a) CV curve of all samples (b) CV curve of CHF-800 at different scan rates.

Moreover, The CV curves of CHF-800 at different scan rates from  $1 \text{ mV s}^{-1}$  to  $5 \text{ mV s}^{-1}$  were shown in the Figure 3b. The rectangular shapes of CV curves were more stable gradually with the increasing scan rates, which had indicated the excellent capacitor behaviour of the carbon electrode materials[28]. Figure 4 was shown the specific capacitance versus the scan rate variations at  $1 \text{ mV s}^{-1}$ ,  $2 \text{ mV s}^{-1}$ ,  $5 \text{ mV s}^{-1}$  and  $10 \text{ mV s}^{-1}$  for all the samples. The increasing scan rates were caused the gradually decreasing specific capacitance. The decreasing specific capacitance was due to a different of factors controlling, including the pore size distribution, a combination of micro-, meso-, and macropores[29,30]. Based on the standard formula which stated the previously, the energy density of CFM-750, CFM-800, CFM-850, and CFM-900 were 28.05, 30.00, 26.67, and  $20.42 \text{ Wh kg}^{-1}$  with power density of 101.08, 108.57, 96.09 and  $73.57 \text{ W kg}^{-1}$ , respectively. These results are similar with other study with different biomass sources such as coffee wastes activated carbon were  $34 \text{ Wh kg}^{-1}$  and  $215 \text{ W kg}^{-1}$ [31] and pistachio shell [32,33] porous carbon was  $39 \text{ Wh kg}^{-1}$  and  $286 \text{ W kg}^{-1}$ .

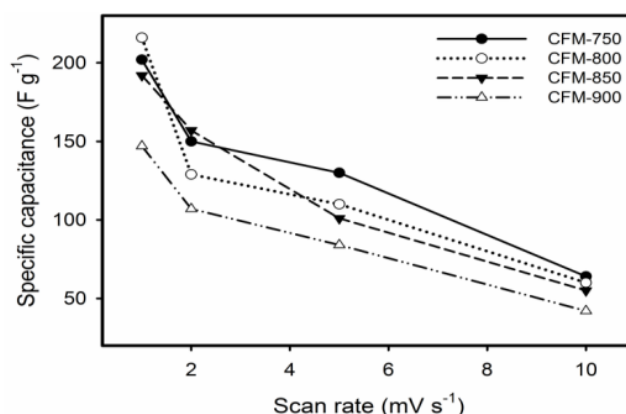

**Figure 4.** The specific capacitance versus the scan rate variation of all samples.

#### 4. Conclusion

In this work, porous activated carbon monolith derived from coconut husk fiber through one-stage integrated pyrolysis and  $\text{ZnCl}_2$  impregnation was successfully demonstrated for electrode supercapacitor. The physical activation temperature was varied including 750, 800, 850 and 900 °C. Generally, different temperatures of physical activation were affected the electrochemical behaviour of symmetric supercapacitor cells. In 750 °C to 800 °C, the specific capacitance is increase from 202 to  $216 \text{ F g}^{-1}$ . However, in higher temperature of 800 °C to 900 °C, the specific capacitance is reduced

from 216 to 147  $\text{F g}^{-1}$ . As a result, CFM-800 can act as a promising material as activated carbon monolith for supercapacitor electrode with the specific capacitances of 216  $\text{F g}^{-1}$  with energy density and power density of 30.00  $\text{Wh kg}^{-1}$  and 108.57  $\text{W kg}^{-1}$ , respectively. Based on these results, the activated carbon monoliths derived from coconut husk fiber are promising as an electrode material through one-stage integrated pyrolysis and  $\text{ZnCl}_2$  impregnation for supercapacitor energy storage.

#### Acknowledgement

This study was funded by DRPM Kemenristek-Dikti through second year Project of PD (396/UN.19.5.1.3/PT.01.03/2020) with the title "High-density micro-and nano carbon fiber made from biomass based materials for supercapacitor electrodes".

#### References

- [1] Statistics S of H 2016 *Statistics of Annual Fruit and Vegetable Plants Indonesia 2015* (Jakarta: BPS-Statistics Indonesia)
- [2] Thinkohkaew K, Rodthongkum N and Ummartyotin S 2020 Coconut husk (*Cocos nucifera*) cellulose reinforced poly vinyl alcohol-based hydrogel composite with control-release behavior of methylene blue *J. Mater. Res. Technol* **9** 6602–11
- [3] Azwar E, Wan Mahari W A, Chuah J H, Vo D V N, Ma N L, Lam W H and Lam S S 2018 Transformation of biomass into carbon nanofiber for supercapacitor application-A review *Int. J. Hydrogen Energy* **43** 20811–21
- [4] Jose J, Thomas V, Vinod V, Abraham R and Abraham S 2019 Nanocellulose based functional materials for supercapacitor applications *J. Sci. Adv. Mater. Devices* **4** 333–40
- [5] Liu Y, Chen J, Cui B, Yin P and Zhang C 2018 Design and Preparation of Biomass-Derived Carbon Materials for Supercapacitors: A Review *C* **4** 53
- [6] Poonam, Sharma K, Arora A and Tripathi S K 2019 Review of supercapacitors: Materials and devices *J. Energy Storage* **21** 801–25
- [7] Zhang G, Chen Y, Chen Y and Guo H 2018 Activated biomass carbon made from bamboo as electrode material for supercapacitors *Mater. Res. Bull* **102** 391–8
- [8] Zhang Y J, Xing Z J, Duan Z K, Li M and Wang Y 2014 Effects of steam activation on the pore structure and surface chemistry of activated carbon derived from bamboo waste *Appl. Surf. Sci* **315** 279–86
- [9] Yang V, Senthil R A, Pan J, Khan A, Osman S, Wang L, Jiang W and Sun Y 2019 Highly ordered hierarchical porous carbon derived from biomass waste mangosteen peel as superior cathode material for high performance supercapacitor *J. Electroanal. Chem* 113616
- [10] Li Y, Wang X and Cao M 2018 Three-dimensional porous carbon frameworks derived from mangosteen peel waste as promising materials for  $\text{CO}_2$  capture and supercapacitors *J. CO2 Util* **27** 204–16
- [11] Ma F, Ding S, Ren H and Liu Y 2019 Sakura-based activated carbon preparation and its performance in supercapacitor applications *RSC Adv* **9** 2474–83
- [12] Chen H, Guo Y C, Wang F, Wang G, Qi P R, Guo X H, Dai B and Yu F 2017 An activated carbon derived from tobacco waste for use as a supercapacitor electrode material *New Carbon Mater* **32** 592–9
- [13] Xia X, Liu H, Shi L and He Y 2012 Tobacco stem-based activated carbons for high performance supercapacitors *J. Mater. Eng. Perform* **21** 1956–61
- [14] Samanta A K, Basu G and Mishra L 2018 Role of major constituents of coconut fibres on absorption of ionic dyes *Ind. Crops Prod* **117** 20–7
- [15] Tan I A W, Ahmad A L and Hameed B H 2008 Adsorption of basic dye on high-surface-area activated carbon prepared from coconut husk: Equilibrium, kinetic and thermodynamic studies *J. Hazard. Mater* **154** 337–46
- [16] Taer E, Taslim R, Putri A W, Apriwandi A and Agustino A 2018 Activated carbon electrode made from coconut husk waste for supercapacitor application *Int. J. Electrochem. Sci* **13** 12072–84
- [17] Li W, Yang K, Peng J, Zhang L, Guo S and Xia H 2008 Effects of carbonization temperatures

- 4 on characteristics of porosity in coconut shell chars and activated carbons derived from carbonized coconut shell chars *Ind. Crops Prod* **28** 190–8
- [18] Sun Q, Jiang T, Zhao G and Shi J 2019 Porous carbon material based on biomass prepared by MgO template method and ZnCl<sub>2</sub> activation method as electrode for high performance supercapacitor *Int. J. Electrochem. Sci* **14** 1–14
- [19] Men B, Guo P, Sun Y, Tang Y, Chen Y, Pan J and Wan P 2019 High-performance nitrogen-doped hierarchical porous carbon derived from cauliflower for advanced supercapacitors *J. Mater. Sci* **54** 2446–57
- [20] Gao Z, Zhang Y, Song N and Li X 2017 Biomass-derived renewable carbon materials for electrochemical energy storage *Mater. Res. Lett* **5** 69–88
- [21] Iro Z S, Subramani C and Dash S S 2016 A brief review on electrode materials for supercapacitor *Int. J. Electrochem. Sci* **11** 10628–43
- [22] Taer E, Dewi P, Sugianto S, Syech R, Taslim R, Salomo S, Susanti Y, Purnama A, Apriwandi A, Agustino A and Setiadi R N 2018 The synthesis of carbon electrode supercapacitor from durian shell based on variations in the activation time *AIP Conf. Proc* **1927**
- [23] Taslim R, Dewi T R, Taer E, Apriwandi A, Agustino A and Setiadi R N 2018 Effect of physical activation time on the preparation of carbon electrodes from pineapple crown waste for supercapacitor application *J. Phys. Conf. Ser* **1120** 012084
- [24] Taer E, Apriwandi A, Krisman, Minarni, Taslim R, Agustino A and Afrianda A 2018 The physical and electrochemical properties of activated carbon electrode made from pandanus tectorius *J. Phys. Conf. Ser* **1120** 012006
- [25] Pandolfo A G and Hollenkamp A F 2006 Carbon properties and their role in supercapacitors *J. Power Sources* **157** 11–27
- [26] Gou G, Huang F, Jiang M, Li J and Zhou Z 2020 Hierarchical porous carbon electrode materials for supercapacitor developed from wheat straw cellulosic foam *Renew. Energy* **149** 208–16
- [27] Zhang Y, Yu S, Lou G, Shen Y, Chen H, Shen Z, Zhao S, Zhang J, Chai S and Zou Q 2017 Review of macroporous materials as electrochemical supercapacitor electrodes *J. Mater. Sci* **52** 11201–28
- [28] Sun Y, Xue J, Dong S, Zhang Y, An Y, Ding B, Zhang T, Dou H and Zhang X 2020 Biomass-derived porous carbon electrodes for high-performance supercapacitors *J. Mater. Sci* **55** 5166–76
- [29] Zhang W L, Xu J H, Hou D X, Yin J, Liu D B, He Y P and Lin H B 2018 Hierarchical porous carbon prepared from biomass through a facile method for supercapacitor applications *J. Colloid Interface Sci* **530** 338–44
- [30] Yang S, Wang S, Liu X and Li L 2019 Biomass derived interconnected hierarchical micro-meso-macro- porous carbon with ultrahigh capacitance for supercapacitors *Carbon N. Y* **147** 540–9
- [31] Kalyani P and Anitha A 2013 Biomass carbon & its prospects in electrochemical energy systems *Int. J. Hydrogen Energy* **38** 4034–45
- [32] Hu C C, Wang C C, Wu F C and Tseng R L 2007 Characterization of pistachio shell-derived carbons activated by a combination of KOH and CO<sub>2</sub> for electric double-layer capacitors *Electrochim. Acta* **52** 2498–505
- [33] Wu F C, Tseng R L, Hu C C and Wang C C 2005 Effects of pore structure and electrolyte on the capacitive characteristics of steam- and KOH-activated carbons for supercapacitors *J. Power Sources* **144** 302–9



# Activated Carbon Monolith Derived from Coconut Husk Fiber as Electrode Material for Supercapacitor Energy Storage

## ORIGINALITY REPORT

15%

SIMILARITY INDEX

5%

INTERNET SOURCES

13%

PUBLICATIONS

5%

STUDENT PAPERS

## PRIMARY SOURCES

- 1

E Taer, A Agustino, R Farma, R Taslim et al. "The relationship of surface area to cell capacitance for monolith carbon electrode from biomass materials for supercapacitor application", *Journal of Physics: Conference Series*, 2018

3%

Publication
- 2

Silu Huo, Xueli Zhang, Bolong Liang, Yubo Zhao, Kexun Li. "Synthesis of interconnected hierarchically porous carbon networks with excellent diffusion ability based on NaNO<sub>3</sub> crystal-assisted strategy for high performance supercapacitors", *Journal of Power Sources*, 2020

1%

Publication
- 3

Bin-Hai Cheng, Raymond J. Zeng, Hong Jiang. "Recent developments of post-modification of biochar for electrochemical energy storage", *Bioresource Technology*, 2017

1%

Publication

4

Internet Source

1 %

5

Hatem A AL-Aoh. " Adsorption of MnO from aqueous solution by powder; kinetic, equilibrium and thermodynamic studies ", Materials Research Express, 2019

Publication

1 %

6

Submitted to University of Pretoria

Student Paper

1 %

7

[www.jmrt.com.br](http://www.jmrt.com.br)

Internet Source

1 %

8

Submitted to Queen's University of Belfast

Student Paper

1 %

9

Meimei Wang, Kuihua Han, Jianhui Qi, Jinxiao Li, Zhaocai Teng, Ming Li.

"Nanoscale/microscale porous graphene-like sheets derived from different tissues and components of cane stalk for high-performance supercapacitors", Journal of Materials Science, 2019

Publication

&lt;1 %

10

M. Karnan, K. Subramani, N. Sudhan, N. Ilayaraja, M. Sathish. " Derived Activated High-Surface-Area Carbon for Flexible and High-Energy Supercapacitors ", ACS Applied Materials & Interfaces, 2016

&lt;1 %

11

Xiaoyan Shi, Jinchao Yu, Qiunan Liu, Lianyi Shao, Yongqi Zhang, Zhipeng Sun, Haitao Huang. "Metal-Organic Framework Derived N, P and O Codoped Nickel/Carbon Composites Homogeneously Decorated on Reduced Graphene Oxide for Energy Storage", ACS Applied Nano Materials, 2020

Publication

<1 %

12

[polen.itu.edu.tr](http://polen.itu.edu.tr)

Internet Source

<1 %

13

J.J Pis, M Mahamud, J.A Pajares, J.B Parra, R.C Bansal. "Preparation of active carbons from coal", Fuel Processing Technology, 1998

Publication

<1 %

14

Soon Yee Liew, Wim Thielemans, Stefan Freunberger, Stefan Spirk. "Polysaccharide Based Supercapacitors", Springer Science and Business Media LLC, 2017

Publication

<1 %

15

[dspace.nm-aist.ac.tz](http://dspace.nm-aist.ac.tz)

Internet Source

<1 %

16

Sanjit Saha, Milan Jana, Pranab Samanta, Naresh C. Murmu, Tapas Kuila. " Efficient Access of Voltammetric Charge in Hybrid Supercapacitor Configured with Potassium

<1 %

# Incorporated Nanographitic Structure Derived from Cotton ( ) as Negative and Ni(OH) /rGO Composite as Positive Electrode ", Industrial & Engineering Chemistry Research, 2016

Publication

17

[www.electrochemsci.org](http://www.electrochemsci.org)

Internet Source

<1 %

18

[www.jurnal.unsyiah.ac.id](http://www.jurnal.unsyiah.ac.id)

Internet Source

<1 %

19

[www.frontiersin.org](http://www.frontiersin.org)

Internet Source

<1 %

20

Li-Feng Chen, Xu-Dong Zhang, Hai-Wei Liang, Mingguang Kong, Qing-Fang Guan, Ping Chen, Zhen-Yu Wu, Shu-Hong Yu. "Synthesis of Nitrogen-Doped Porous Carbon Nanofibers as an Efficient Electrode Material for Supercapacitors", ACS Nano, 2012

Publication

<1 %

21

[www.scientific.net](http://www.scientific.net)

Internet Source

<1 %

22

Yuli Yetri, Anh Tuan Hoang, Mursida, Dahyunir Dahlan, Muldarisnur, Erman Taer, Minh Quang Chau. "Synthesis of activated carbon monolith derived from cocoa pods for supercapacitor electrodes application", Energy Sources, Part A: Recovery, Utilization, and Environmental

<1 %



23

Xuan Bai, Feng Zhang, Yibo Wang, Bin Zhai, Yu Song, Xiuying Wang, Jun Zhao. "The effects of anions on the structure and the electrochemical performance of carbon materials for supercapacitors", Journal of Physics and Chemistry of Solids, 2020

Publication

<1 %

24

Jianhua Hou, Chuanbao Cao, Faryal Idrees, Xilan Ma. "Hierarchical Porous Nitrogen-Doped Carbon Nanosheets Derived from Silk for Ultrahigh-Capacity Battery Anodes and Supercapacitors", ACS Nano, 2015

Publication

<1 %

25

Yannan Lin, Hongxia Zhao, Feng Yu, Jinfeng Yang. "Design of an Extended Experiment with Electrical Double Layer Capacitors: Electrochemical Energy Storage Devices in Green Chemistry", Sustainability, 2018

Publication

<1 %

26

Shu-Xia Liang, Fang-Fang Duan, Qiu-Feng Lü, Haijun Yang. "Hierarchical Biocarbons with Controlled Micropores and Mesopores Derived from Kapok Fruit Peels for High-Performance Supercapacitor Electrodes", ACS Omega, 2019

Publication

---

<1 %

27

Luiz K. C. de Souza, João Carlos Martins, Diogo Padilha Oliveira, Carlos Sergio Ferreira et al. "Hierarchical porous carbon derived from acai seed biowaste for supercapacitor electrode materials", Journal of Materials Science: Materials in Electronics, 2020

Publication

<1%

28

Lin Qian, Feiqiang Guo, Xiaopeng Jia, Yinbo Zhan, Huiming Zhou, Xiaochen Jiang, Chao Tao. "Recent development in the synthesis of agricultural and forestry biomass-derived porous carbons for supercapacitor applications: a review", Ionics, 2020

Publication

<1%

Exclude quotes On

Exclude matches Off

Exclude bibliography On